

## **METRIC**





0

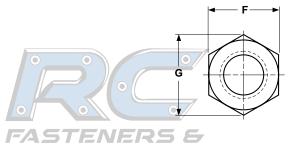

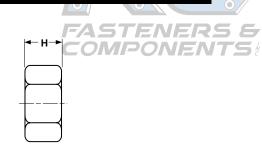

METRIC - Hex Nuts, Style 2						
		I	F	G		+
Nominal Size	Thread Pitch	Width Across Flats		Width Across Corners	O Thickness	
		Мах	Min	Min –		<b>ER</b> Min <b>E</b>
M5	0.8	8	7.78	8.79	5.1	4.8
M6	1	10	9.78	11.05	5.7	5.4
M8	1.25	13	12.73	14.38	7.5	7.14
M10	1.5	16	15.73	17.77	9.3	8.94
M12	1.75	18	17.73	20.03	12	11.57
M14	2	21	20.67	23.35	14.1	13.4
M16	2	24	23.67	26.75	16.4	15.7
M20	<b>1</b> PQ.5		29.16	32.95	20.3	19
M24	3	36	35	39.55	23.9	22.6
M30	3.5	46	45	50.85	28.6	27.3
M36	4	55	53.8	60.79	34.7	33.1





FAS	ENERS &		
Description	A six-sided internally threaded, heat treated fastener with a metric thread pitch. Style 2 nuts are approximately 10% thicker than Style 1 nuts of the same nominal diameter. Nuts M16 and smaller are chamfered on the top and the bearing surface. Nuts M18 and larger may be either double chamfered, or have a washer face on one side and a chamfered surface on the opposite side.		
Applications/ Advantages	Class 12 nuts are intended for use with screws and bolts of property classes 12.9 or lower.		
Material	Class 12 nuts shall be made of a steel which conforms to the following chemical composition <i>Carbon:</i> 0.58% maximum; <i>Manganese:</i> 0.45% minimum; <i>Phosphorus:</i> 0.048% maximum; <i>Sulfur:</i> 0.058% maximum.		
Heat Treatment	Class 12 nuts shall be heat treated by quenching in a liquid medium from a temperature above the transformation temperature and tempering at a temperature of at least 425°C.		
Hardness	Style 1: Vickers HV 295 - 353 (Rockwell C 29.2 - 36)   Style 2: Vickers HV 272 - 353 (Rockwell C 25 - 36)		
Proof Load	Style 1: Diameters M1.6 through M10: 1140 N/mm²; Diameters M12 through M16: 1170 N/mm²   Style 2: Diameters M1.6 through M7: 1150 N/mm²; Diameters M8 through M10: 1160 N/mm²;   Diameters M12 through M16: 1190 N/mm²; Diameters M18 through M36: 1200 N/mm²		
Plating	<b>ENERS 5</b> See Appendix-A for plating information		
	PONENTS		

UNENIS