


Flat Point

METRIC Socket Set Screws







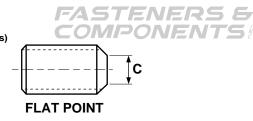

COMP METRIC - SOCKET SET SCREW, FLAT POINT ISO 4026 & 898/5											
Nominal Size	Thread Pitch	C Point Diameter		Е	S Socket Size Across the Flats		Screws Below this Length are Short Sizes	T Key Engagement (Min)			
				Socket Size Across Corners							Test Torque
		Max	Min	Min	Max	Min	0.200	Short Sizes	Long Sizes	NEN	N. m
M1.6	0.35	0.80	0.55	0.803	0.724	0.711	2.5	0.7	1.5	-	-
M2	0.4	1.00	0.75	1.003	0.902	0.889	3	0.8	1.7	-	-
M2.5	0.45	1.50	1.25	1.427	1.295	1.270	4	1.2	2	-	-
M3	0.5	2.00	1.75	1.73	1.545	1.520	4	1.2	2	4	0.9
M4	0.7	2.50	2.25	2.3	2.045	2.020	5	1.5	2.5	5	2.5
M5	0.8	3.5	3.2	2.87	2.560	2.520	6	2	3	5	5
M6	1	4.0	3.7	3.44	3.071	3.020	8	2	3.5	8	8.5
M8	1.25	5.5	5.2	4.58	4.084	4.020	8	3	5 0	8	20
M10	1.5	7.00	6.64	5.72	5.084	5.020	10	4	6	10	40
M12	1.75	8.50	8.14	6.86	6.095	6.020	16	4.8	8	16	65
M16	2	12.00	11.57	9.15	8.115	8.025	20	6.4	10	20	160
M20	2.5	15.00	14.57	11.43	10.115	10.025	20	8 = /	512 E	20 = 0	310
M24	3	18.00	17.57	13.72	12.142	12.032	25	10	15	25	520
					·					1	
Tolerance on Length			2-3mm: ±0.2		4-6mm: ±0		.24 8-10mn		n: ±0.29 12-16mm: ±0.35		: ±0.35
			20-30mm: ±0.42			35-50mm: ±0.5			55-60mm: ±0.6		

FASTENERS &

Description	A headless screw threaded the entire length with a metric thread pitch. It has a flat surface at the end opposite that of the hexagonal drive.
Applications/ Advantages	Flat point set screws are designed for frequent resetting or relocating on hard steel shafts and where minimal damage to shafts is a concern.
Material	Metric socket set screws shall be made from an alloy steel which conforms to the following chemical composition requirements- Carbon: 0.19-0.50%; Phosphorous: 0.05% maximum; Sulfur: 0.05% maximum; Lead: 0.35% maximum. Set screws shall also contain one or more of these following elements: chromium, nickel, molybdenum, vanadium or boron.
Heat Treatment	Metric socket set screws shall be heat treated by quenching in oil from above the transformation temperature and then tempered by reheating to meet the hardness requirements listed below.
Hardness	Rockwell HRC 45 - 53 (Vickers HV 450 - 560)
Torsional Strength	Metric socket set screws of a sufficient length to be tested (as listed in the above table) shall withstand application of the test torque specified in said table without evidence of the socket reaming or the screw bursting.
Plating	Metric socket set screws are usually supplied with a thermal black finish.